arXiv:cond-mat/0504552v1 [cond-mat.str-el] 21 Apr 2005

Possible canted antiferromagnetism in UCu_9Sn_4

U. Killer [a] E.-W. Scheidt [a] H. Michor [b] J. Hemberger [c] H.A. Krug von Nidda [c] W. Scherer [a]

[a] *Chemische Physik und Materialwissenschaften, Universität Augsburg, 86159 Augsburg, Germany*
[b] *Institut für Festkörperphysik, TU Wien, 1040 Wien, Austria*
[c] *EP V, Elektronische Korrelationen und Magnetismus, Institut für Physik, Universität Augsburg, 86159 Augsburg, Germany*

Abstract

We report on the new compound UCu_9Sn_4 which crystallizes in the tetragonal structure $I4/mcm$ with lattice parameters $a = 8.600$Å and $c = 12.359$Å. This compound is isotyp to the ferromagnetic systems $RECu_9Sn_4$ (RE = Ce, Pr, Nd) with Curie temperatures $T_C = 5.5\,K$, 10.5 K and 15 K, respectively. UCu_9Sn_4 exhibits an uncommon magnetic behavior resulting in three different electronic phase transitions. Below 105 K the sample undergoes a valence transition accompanied by an entropy change of 0.5 Rln2. At 32 K a small hump in the specific heat and a flattening out in the susceptibility curve probably indicate the onset of helical spin order. To lower temperatures a second transition to antiferromagnetic ordering occurs which develops a small ferromagnetic contribution on lowering the temperature further. These results are strongly hinting for canted antiferromagnetism in UCu_9Sn_4.

Key words:
valence transition, canted antiferromagnetism

Recent studies on ternary compounds like $CeNi_9Ge_4$ [1] and $RECu_9Sn_4$ (RE = Ce, Pr, Nd) [2] have attracted much interest because of their manifold electronic and magnetic properties. In the non-Fermi liquid (nFl) system $CeNi_9Ge_4$ we observed the largest ever recorded value of the electronic specific heat $\Delta c/T \approx 5.5\,J\,K^{-2}mol^{-1}$ without presence of any trace of magnetic order [1] that is mainly based on single ion effects [3]. Long range ferromagnetic order was found in $RECu_9Sn_4$ (RE = Ce, Pr, Nd) with Curie temperatures T_C of 5.5 K, 10.5 K and 15 K, respectively [2]. These systems crystallize in the tetragonal structure $I4/mcm$ with large RE-RE spacings of about 6.1 Å while the corresponding Ce-Ce distances in $CeNi_9Ge_4$ value at 5.548 Å. In this work we focus on the new isotyp compound UCu_9Sn_4 which is on the borderline between long range magnetic order and nFl behavior due to the expanded 5f-electron orbitals. The X-ray powder pattern of annealed (650°C for one week) polycrystalline UCu_9Sn_4 also adopts the tetragonal structure ($I4/mcm$) with $a = 8.600$Å and $c = 12.359$Å which are comparable to the lattice parameters of $RECu_9Sn_4$. The *dc*-susceptibility of UCu_9Sn_4 exhibits two pronounced transitions at 105K and 22K (Fig. 1). Above 105 K the susceptibility follows a Curie-Weiss law with μ_{eff}=2.9μ_B which is in between the f^1 and f^2 state of Uranium. The upper transition at 105 K, which is independent of magnetic field, gives rise to a peak in specific heat (Fig. 2). A little anomaly is observed in resistivity measurements as well. The entropy of this anomaly (Fig. 2B) is half of that of an antiferromagnetic transition with effective spin of 1/2 ($\Delta S = 0.5R\ln 2$) indicating a valence transition from the mixed f^1/f^2 to f^1 state. This is confirmed by the magnetic entropy of $S = R\ln 4$ which is the same as for Ce $4f^1$ in $CeNi_9Ge_4$. The expected moment of $2.54\mu_B$ is masked by strong magnetic fluctuations below 60 K (see Fig. 2A).

Below 32 K the antiferromagnetic fluctuation tends to long range magnetic order visualized by forming out a shoulder in the susceptibility (arrows in Fig. 1A/B and Fig. 2A). The significant feature in the specific

---

[1] This work was supported by the SFB 484 of the Deutsche Forschungsgemeinschaft (DFG).

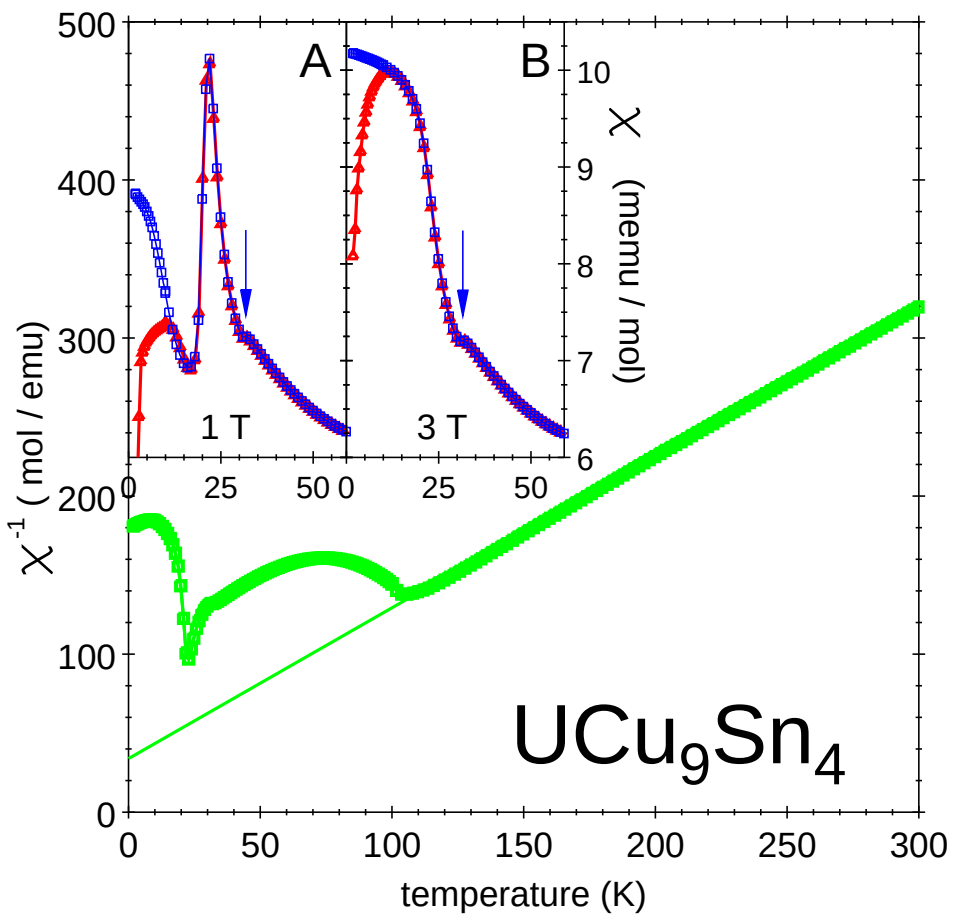

Fig. 1. Inverse magnetic dc susceptibility of UCu$_9$Sn$_4$ versus temperature measured in a magnetic field of 0.5 T.The straight line represents a Curie-Weiss fit to the data above 105 K. The insert shows dc-χ zero-field (ZFC) / field cooled (FC) splitting in A) $B = 1$ T and B) $B = 3$ T

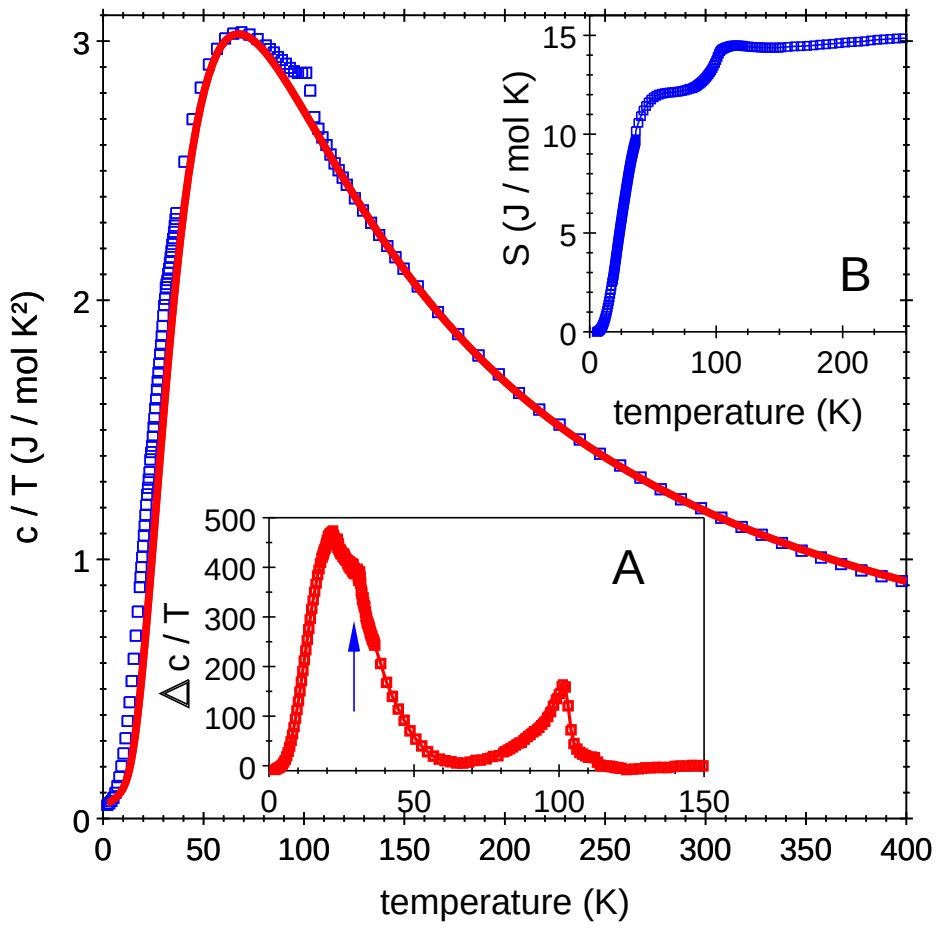

Fig. 2. The specific heat divided by temperature vs. temperature of UCu$_9$Sn$_4$. The solid line is a calculation of the phonon contribution using a Debye and two Einstein terms. A) The electronic contribution to the specific heat $\Delta c/T$. Notice the 3 anomalies at 22 K, 32 K and 105 K. B) The entropy of the magnetic contribution $S = R \ln 4$ per U-mol at 50 K indicates two low lying doublets also found in CeNi$_9$Ge$_4$.

heat and the magnetic field independent transition indicate a helimagnetic phase [4]. On decreasing temperature the sharp peak in the dc-χ is characteristic for a second transition into a commensurate antiferromagnetic structure. This is also confirmed by phonon adjusted $\Delta c/T$ data (Fig. 2A) where spin-reorientation is observed at 22 K.

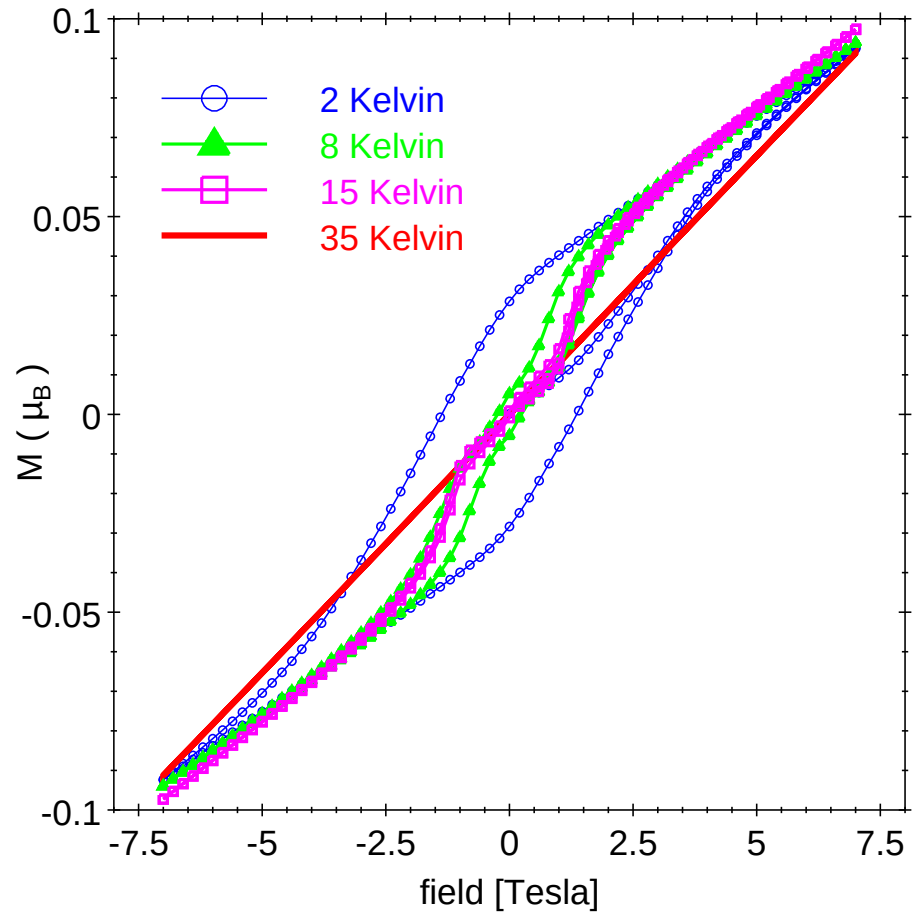

Fig. 3. Metamagnetic behavior and the formation of the canted antiferromagnetic phase below 8 K of UCu$_9$Sn$_4$.

With increasing magnetic field a slight ferromagnetic contribution develops at low temperature indicating a sign of a canted anitferromagnetic state. At high fields ($\geq$3 T) a transition from the paramagnetic straight into the canted state occurs already at 32 K (Fig. 1B). In Fig. 3 the magnetic hysteresis corroborates the crossover form pure to canted antiferromagnetism with a spin-flop transition at 15 K and the opening of a hysteresis loop below 8 K with a spontaneous moment of $M_{\rm sat} \approx 0.03 \mu_{\rm B}$.

The ZFC/FC splitting in dc-χ (Fig. 1A/B) may be explained by forming spontaneous small ferromagnetic domains in the canted antiferromagnetic phase below 8 K. In this temperature range the ferromagnetic domains are growing in an external magnetic field. On the occasion of the strong spin-orbit coupling of uranium atoms the domain walls exhibit a large inertia. The absence of any frequency shift of the transition maximum in ac-χ measurements rules out frustration effects.

Summarizing three distinguished phase transitions are observed in UCu$_9$Sn$_4$: i) valence shift at 105 K, ii) onset of helimagnetic order at 32 K, and iii) transition into commensurate antiferromagnetic structure at 22 K with magnetic field induced canting.

References

[1] H. Michor *et al.*, J. Mag. Mag. Mat. **272-276**, (2004) 227.

[2] S. Singh*et al.*, J. Alloys Comp. 317-318 (2001) 560-566.

[3] U. Killer *et al.*, cond-mat/0402498.

[4] J. Hemberger *et al.*, cond-mat/0311249.